

STRUCTURAL PROPERTIES OF MICRO AND NANO-STRUCTURED AMORPHOUS CARBON FILMS FROM LIQUID HYDROCARBON PRECURSOR IN PHOTOVOLTAIC HETERO JUNCTION SOLAR CELL APPLICATIONS

^{1,3}A. Ishak, ^{1,2}M. Rusop

¹NANO-ElecTronic Centre, Faculty of Electrical Engineering, UniversitiTeknologi MARA, Shah Alam, Selangor, Malaysia

²NANO-SciTech Centre, Institute of Science, UniversitiTeknologi MARA,
40450 Shah Alam, Selangor, Malaysia

³Faculty of Electrical Engineering, UiTM Sarawak, Kampus Kota Samarahan, JalanMeranek, Sarawak

Abstract- The micro-structured of as-deposited (a-C) and nano-structured boron-doped amorphous carbon (a-C:B) films prepared from natural palm oil precursor for heterojunction solar cell were presented. Field-emission scanning electron microscopy (FESEM) revealed the micro and nano structured films had particle size in the range of 382 nm to 689 nm and 28 to 34 nm, respectively. The energy-dispersive spectroscopy (EDS) showed the existing of carbon in micro-structured amorphous carbon film and carbon together with boron in nano-structured amorphous carbon film. Solar simulator analysis results showed an open circuit voltage (V_{OC}), current density (J_{SC}), fill-factor(FF) and conversion efficiency (η) of Au/a-C/n-Si/Au were 264.62 mV, 1.50434 mA/cm², 0.32632, and 0.130154 %, respectively. Meanwhile, the V_{OC} , J_{SC} , FF and η of Au/a-C:B/n-Si/Au solar cell were 271.25mV, 14.91723 mA/cm², 0.33582, and 1.542622 %, respectively. The conversion efficiency was increased as constant negative bias of -20 V applied for doping boron into a-C film.

Keywords-Amorphous carbon; Palm-oil; Negative bias; Boron doping; Carbon; Carbon solar cell

I. INTRODUCTION

Many types of carbon precursors have been discovered from renewable precursors; camphor powder, turpentine oil, coconut oil, etc [1,2] and non-renewable sources; methane, acetylene, ethanol and ethylene for producing allotrope carbon such as carbon nano tubes (CNT), graphene, amorphous carbon, etc. using various method of depositions [1,2]. Beside of those precursors, palm oil the other abundantly promising 'green' source was successfully synthesized the vertically aligned carbon nanotubes (VACNTs). Palm oil is scientifically known as hexanoic acid which was derived from fibrous exocarp and mesocarp of the fruits of palm tree. The palm oil is contained carbon (67), hydrogen (127) and oxygen (8) to form the chemical binding of C₆₇H₁₂₇O₈ (3). This compound has the highest carbon content among the known precursors. The synthesizing of a-C on the other hand, required less energy compared with other allotropes carbon for instant, the VACNTs need deposition temperature above 700°C[1]. Nevertheless, the a-C films are weak p-type in nature and they possess complex structure and high density of defects, thereby restricting their doping capacity; this low doping efficiency is the main obstacle for their application in various electronic devices. Amorphous carbon (a-C) films have gained considerable attention because of their controllable optical gap, which allows for its wide application in the manufacture of semiconductors. In order to solve that problem, it was suggested; the control of doping could reduce

the existing of defect and at the same time modified the electronic properties [3-5].

Among deposition parameters, negative bias voltage applied to the substrates could significantly change film properties due to enhancement of adatom mobility and the effects of ion bombardment. The ion bombardment during coating deposition would play an important role in affecting the morphology, structure, composition and mechanical properties of coatings [6,7]. Many attempts were studied by others on the effect of negative bias for instant through the use of pure lubricant coatings (MoS₂) composite film. It was reported that, the increase of bias caused preferential re-sputtering of S resulting in a reduced S/Mo ratio, which can affect different properties of the film. A reported study on pure MoS_x films deposited by bipolar pulsed DC showed that even an S/Mo ratio of 0.8 was able to provide good lubricious property due to the strong basal plane orientation and application of a bias voltage was found to reduce the coefficient of friction[8-10]. Therefore, an understanding of substrate bias effects is necessary to improve the physical and mechanical properties of MoS₂-based coatings but also important for structural, electrical as well as electronic properties of any semiconductor film.

In this paper, we report the micro-structured of as-deposited and nano-structured of boron doped amorphous carbon films deposited by using deposition temperature without bias (0 V) and deposition temperature with the help of a constant

Publication History

Manuscript Received : 25 April 2014
Manuscript Accepted : 28 April 2014
Revision Received : 29 April 2014
Manuscript Published : 30 April 2014

incorporation of boron in the a-C network and the formation of a-C:B bonding groups.

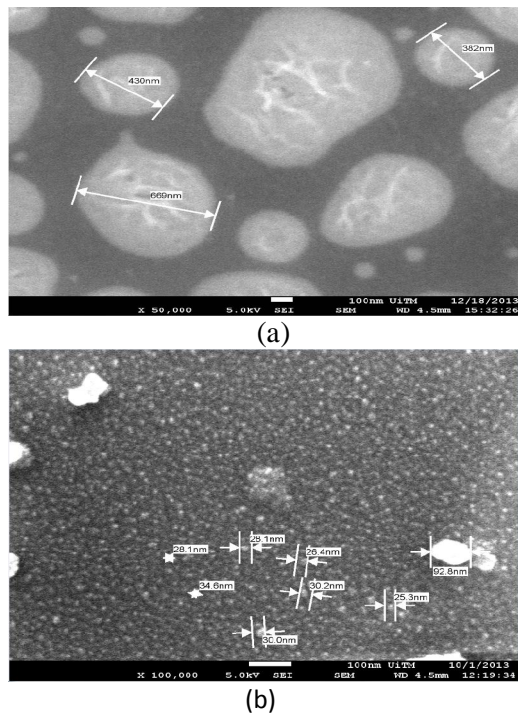


Fig.3 FESEM images of (a) as-deposited (a-C) and (b) boron-doped of a-C:B films

The negative bias of -20 V increases the energy of the bombarding ions, enhancing the chemical reactions between different species and their mobility at the growing film surface. As a result, the high-energy gas ions dissociate the deposition carbon clusters affecting the boron distribution, and the bonding structure of the a-C:B film. Accordingly, without bias voltage (0 V) applied to substrate, the ions energy is too weak to penetrate into the growing surface and most of the ions are only trapped on the growing surface, resulting in the formation of the loose cross-linking [10,11] resulting to the irregularly scattered micro ball-like of agglomerated particles.

Fig. 4 (a) and (b) show the EDS images of micro-structured a-C film and nano-structured a-C:B film, respectively. The composition of carbon arise at 0.4K eV in a-C film while composition of boron together with carbon in a-C:B film arise at around 0.4 and 0.3K eV, respectively. We observed the compositional element of carbon is quite similar with the compositional element of silicon and only small number of oxygen found in is EDS result. In contrast, the compositional element of carbon decrease as boron introduce in a-C film. With negative bias (in this case -20 V), the ion current drew towards the substrate increases along with the flux of neutral and charged species. This further cause an increase in preferential nucleation sites so that individual grain growth is arrested, hence expected to reduce the grain size as shown in Fig. 3 (b). However, the content of the elements are decreased, which possible allowed the grains to expand, since with increase in dopant content, the crystallite size of a-C:B film decrease. The same phenomena were

reported [6,12,13] for TiN-MoS_x and CrB₂-MoS_x composite coating when the increasing of negative bias.

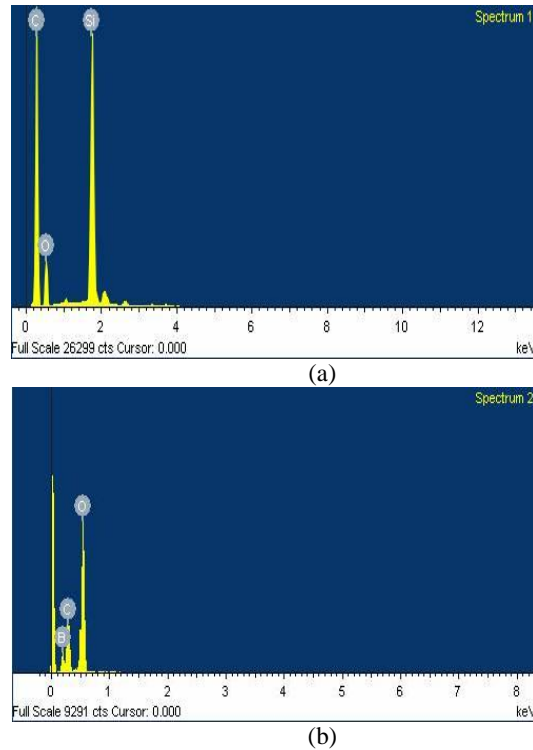


Fig.4 EDS results of (a) as-deposited (a-C) and (b) boron-doped of a-C films

AFM images shown in Fig. 5 illustrate the effect of the bias voltage and without bias voltage on the surface roughness and feature. The films deposited at all conditions show very smooth with agglomerated ‘island’ form. The films deposited without bias (0 V) are denser as compared to negative bias of -20 V but more higher of surface roughness as compared with the applied of negative bias voltage (-20 V) as shown in Table 1. In the case of applied the substrate without negative bias (0 V), the denser of particle at atomic level is attributed by the combination of unwanted macro-particles and neutral atoms. Most of the unwanted macro-particles and neutral atoms are remained under deposition temperature at 350°C. While the surface of a-C:B film became smoother with applied of negative bias (-20 V), resulting in an obvious reduction in surface roughness from 7.605 nm to 0.386 nm. The decreasing tendency of surface roughness with increasing of negative bias voltage can be suggested by the energy of impinging ions to the growing film that help improve the roughness by the surface diffusion [10,14].

Table 1. Surface roughness of micro-structured of a-C film and nano-structured of a-C:B film

Bias voltage (V)	Surface roughness (nm)
0	7.605
-20	0.386

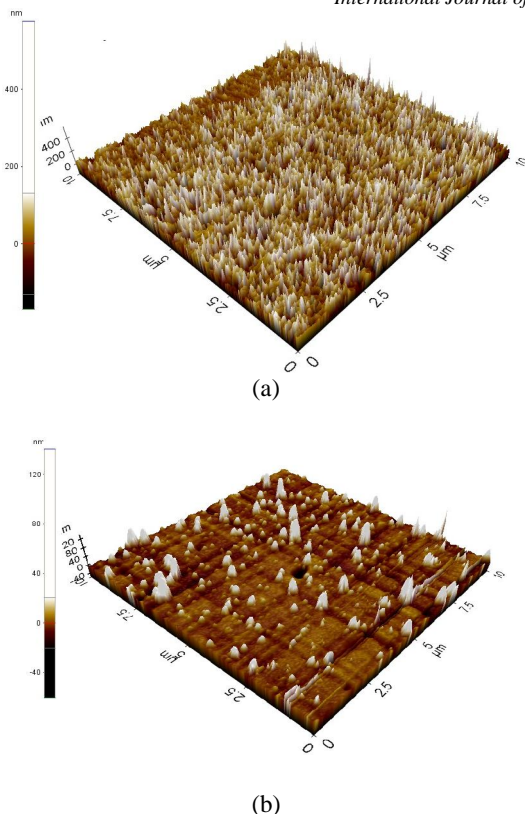


Figure 5 Two typical 3-dimensional AFM images of (a) as-deposited a-C film and (b) boron doped a-C film

The current density-voltage (J - V) characteristics of Au/a-C/n-Si/Au and Au/a-C:B/n-Si/Au solar cells in dark environment are shown in Fig. 6 (a). The Au/a-C/n-Si/Au and Au/a-C:B/n-Si/Au solar cells display rectifying curves, which indicate the formation of heterojunction between the a-C:B film and silicon. The a-C and a-C:B layers acted as a p -type semiconductor with respect to silicon substrate, thus forming the rectifying curve. The reverse saturation current, which is low as compared with the forward current, gradually increases with reverse bias (photocurrent increases). These behaviors can be attributed to the generation of minority carriers within the depletion region. At forward bias, the current increases exponentially, indicating a good quality of p - n junction. The ideality factor is approximately 2, indicating the dominance of the recombination current rather than the diffusion current. Many deviations from the ideal p - n characteristics are observed, which can be due to the high low doping efficiency and possess complex structure and high density of defects [14,15,16].

The I - V characteristics of Au/a-C/n-Si/Au and Au/a-C:B/n-Si/Au devices under illumination at 100 mW/cm^2 are illustrated in Fig. 6 (b). A dissimilar trends in the form of curves are observed for micro-structured film used for Au/a-C/n-Si/Au solar cell and nano-structured film used for Au/a-C:B/n-Si/Au solar cells by the. The obtained curve of Au/a-C/n-Si/Au solar cell is less broad and small area as compared with the obtained curve of Au/a-C:B/n-Si/Au solar cell.

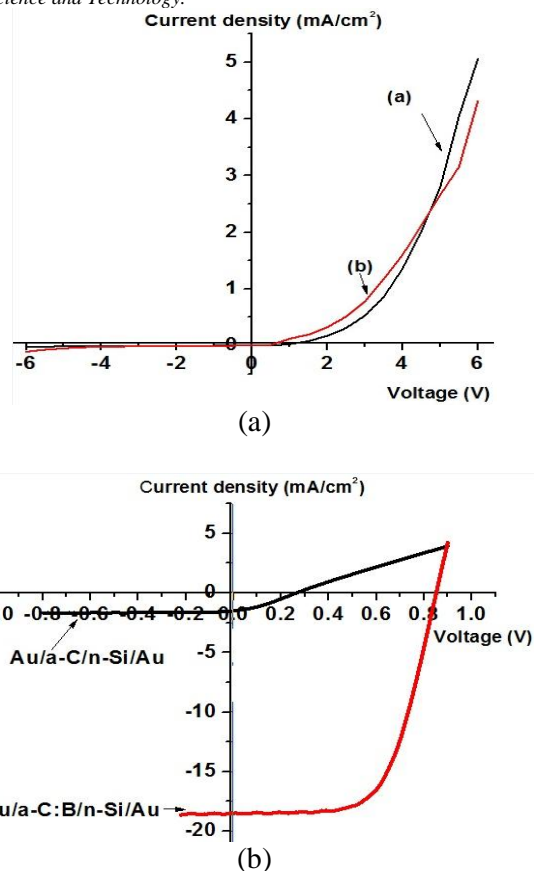


Figure 6 The Au/a-C/n-Si/Au and Au/a-C:B/n-Si/Au solar cells under dark and illumination at 0 V and -20 V

A slightly broad curve indicates reduced area (fill factor, FF) or maximum output power, and thus, the overall conversion efficiency is minimized. This phenomenon is attributed to series and shunt resistances, which are caused by metal contact and material defect, respectively. The open circuit voltage (V_{oc}), current density (J_{sc}), fill factor (FF) and efficiency (η) of Au/a-C/n-Si/Au is V_{oc} , J_{sc} , FF and η is 0.265V, 1.505 mA/cm^2 , 0.327, and 0.1302 %, respectively. Meanwhile, the V_{oc} , J_{sc} , FF and η were 0.272 V, 14.9 mA/cm^2 , 0.336, and 1.543 %, respectively. It was observed that nano-structured a-C:B film used as the p -type in heterojunction solar cell produces higher conversion efficiency than micro-structured a-C film.

The series resistance results in voltage drop, thus preventing full photovoltaic voltage across the external load; likewise, series resistance affects open circuit voltage (V_{oc}) [25, 31]. By contrast, internal resistance of material (shunt resistance) is due to the device edges and grain boundaries [14-16]. Shunt resistance significantly contributes to the reduction of solar cell performance. In shunt resistance, a fraction of photo-generated carriers are diverted away from the external load, thereby reducing current density (J_{sc}). Series resistance can be minimized by introducing metal contact based on grid metal arrangement in commercialized silicon solar cells. Although metal contact arrangement in the solar cell configuration in the present study is attributed to high series resistance, which reduces the overall solar cell efficiency, our objective is to prove the nano-structured a-C

film doping with boron from hydrocarbon source of natural palm oil can also be applied in the fabrication of heterojunction solar cells.

The electronic properties of Au/a-C/n-Si/Au solar cell, including its open V_{oc} , J_{sc} , FF, and efficiency are presented in Fig. 6 (b). Low V_{oc} and J_{sc} are found for micro-structured a-C film, which directly indicate low FF and conversion efficiency. The low V_{oc} and J_{sc} values are attributed to the low built-in voltage, which are caused by the high amount of defect in the micro-structured a-C film. The electronic properties of Au/a-C:B/n-Si/Au solar cells remarkably improved by the increase in the DC bias of the substrate. The Au/a-C:B/n-Si/Au solar cells fabricated through the deposition at -20 V applied bias shows the highest conversion efficiency. The improvement of conversion efficiency can be attributed to the successful boron incorporation, which increases the number of excess carriers in the nano-structured a-C:B film. The bombardment of ions produced by -20 V is important in minimizing defects. The reduction of defects increases the built-in voltage, thereby prolonging the lifetime of excess carriers and providing wide diffusion. Although the energy-conversion efficiencies of the fabricated solar cell devices are considerably low, the present study presents a viable alternative through the use of natural palm oil precursor in developing solar cells. Moreover, the energy-conversion efficiency achieved in this study (deposition at -20 V applied bias) is higher than that reported by Tian. ($\eta = 0.3$ %) [16] and Hayashi, ($\eta = 0.04$ %) [17].

IV. CONCLUSIONS

The micro and nano-structured of a-C and a-C:B films using novel precursor of palm oil for solar cell applications was presented. FESEM revealed films deposited with negative bias of -20 V had small particle in nano-size in the range of 28-52nm. The EDS showed the existing of carbon in micro-structured a-C film and boron with carbon in nano-structured a-C:B film. Negative DC bias can improved the structural properties of the nano-structured size a-C:B films and showed the significant increment of energy conversion efficiency by the ion bombardment effect of the negative bias (-20 V). Solar simulator analysis results showed an open circuit voltage (V_{oc}), current density (J_{sc}), fill-factor(FF) and conversion efficiency (η) of Au/a-C/n-Si/Au were 264.62 mV, 1.50434 mA/cm², 0.32632, and 0.130154 %, respectively. Meanwhile, the V_{oc} , J_{sc} , FF and η of Au/a-C:B/n-Si/Au solar cell were 271.25 mV, 14.91723 mA/cm², 0.33582, and 1.542622 %, respectively. The conversion efficiency was increased as constant negative bias of -20 V applied for doping boron into a-C film. Although the conversion efficiency of heterojunction solar cells are considerably low, it shows a prospect of using palm oil as the carbon source of the nano and micro-structured a-C film for the improvement of the energy conversion efficiency by optimizing the deposition conditions.

ACKNOWLEDGEMENT

The authors thank to Ministry of Higher Education (MOHE) Malaysia, Universiti Teknologi MARA, Kota Samarahan Sarawak for the scholarship, and Research Management Institute (RMI) Universiti Teknologi MARA (UiTM) for the facilities.

REFERENCES

- [1] A.B. Suriani, A.A. Azira, S.F. Nik, Roslan Md Nor, and M. Rusop, Synthesis of vertically aligned carbon nanotubes using natural palm oil as carbon precursor, *Material Letters* 63 (2009) 2704-2706.
- [2] S. Paul, and S.K. Samdarshi, A green precursor for carbon nanotube synthesis, *New Carbon Materials* 26 (2011) 85-88.
- [3] J. Podder, M. Rusop, T. Soga, T. Jimbo, Boron doped amorphous carbon films grown by r.f. PECVD under different partial pressure, 14 (2005) 1799-1804.
- [4] Dayana Kamaruzaman, Nurfadzilah Ahmad, Ishak Annuar, and Muhamad Rusop, Semiconducting Properties of Nanostructured Amorphous Carbon Thin Films Incorporated with Iodine by Thermal chemical Vapor Deposition, *Japanese Journal of Applied Physics* 52 (2013) 11.
- [5] Rusop, M., et al., Effect of Boron Weight Percentages in the Target of Pulsed Laser Deposition on the Preparation of Boron-Doped Amorphous Carbon Films. *Surface Review and Letters*, 12 (2005) 27-34.
- [6] S. Gangopadhyay, R. Acharya, A. K. Chattopadhyay, S. Paul, Effect of substrate bias voltage on structural and mechanical properties of pulsed DC magnetron sputtered TiN-MoS_x composite coatings 84 (2010) 843-850.
- [7] S. Kassavetis, S. Laskarakis, S. Logothetidis, Effect of ion bombardment and hydrogen pressure during deposition on the optical properties of hydrogenated amorphous carbon thin films, 20 (2011) 109-114.
- [8] Xiufeng Tang, fa luo, fang Ou, Wangcheng Zhou, Dongmei Zhu, and Zhibin Huang, Effect of negative bias substrate voltage on the structure and properties of aluminium oxide films prepared by DC reactive magnetron sputtering, *applied surface Science* 259 (2012) 448-453.
- [9] A. Bubenzer, B. Dischler, G. Brandt, P. Koids, rf-plasma deposited amorphous hydrogenated hard carbon thin films: preparation, properties, and applications, *Journal of applied Physics* 54 (1983) 4590.
- [10] Peng Wang, Xia Wang, Youming Chen, Guangan Zhang, Weimin Liu, Junyan Zhang, The effect of applied negative bias voltage on the structure of Ti-doped a-C:h films deposited by FCVA, *Applied Surface Science* 253 (2007) 3722-3726.
- [11] E. Liu, L. Li, B. Blainpain, Residual stresses of diamond and diamondlike carbon films, *Journal of Applied Physics*, 98 (2005) 073515.
- [12] F. Buebuel, I. Efeoglu, E. Arslan, The effect of bias voltage and working pressure on S/Mo ratios at MoS₂-Ti composite films, *Applied Surface Science* 253 (2007) 44515-9.
- [13] M. Sakaki, T. Sakakibara, Ionization and reaction mechanism of a reactive cathodic arc deposition of TiN. *IEEE Trans Plasma Science* (1994) 22.
- [14] M. S. Leu, S. Y. Chen, J. J. Chang, et al. Diamond-like coatings prepared by the filtered cathodic arc technique for minting application, *Surface Coating Technology* 566 (2004) 177-178.
- [15] Rusop, M., et al., Preparation and characterization of boron-incorporated amorphous carbon films from a natural source of camphoric carbon as a precursormaterial, *Applied Surface Science*, 252 (2005) 1693-1703.
- [16] X. M. Tian, M. Rusop, Y. Hayashi, T. Soga, T. Jimbo, and M. Umeno, A photovoltaic cell from p-type boron-doped amorphous carbon film, *Solar Energy Materials and Solar Cells* 77 (2003) 105-112.
- [17] Y. Hayashi, S. Ishikawa, T. Soga, M. Umeno, and T. Jimbo, Photovoltaic characteristics of boron-doped hydrogenated amorphous carbon on n-Si substrate prepared by r.f. plasma-enhanced CVD using trimethylboron, *Diamond and Related Materials* 12 (2003) 687-690.